



Notch Fatigue Strength of a PM Disk Superalloy

*John Gayda, Timothy P. Gabb, and Jack Telesman
Glenn Research Center, Cleveland, Ohio*

NASA STI Program . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) program plays a key part in helping NASA maintain this important role.

The NASA STI Program operates under the auspices of the Agency Chief Information Officer. It collects, organizes, provides for archiving, and disseminates NASA's STI. The NASA STI program provides access to the NASA Aeronautics and Space Database and its public interface, the NASA Technical Reports Server, thus providing one of the largest collections of aeronautical and space science STI in the world. Results are published in both non-NASA channels and by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA counterpart of peer-reviewed formal professional papers but has less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.

- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or cosponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services also include creating custom thesauri, building customized databases, organizing and publishing research results.

For more information about the NASA STI program, see the following:

- Access the NASA STI program home page at <http://www.sti.nasa.gov>
- E-mail your question via the Internet to help@sti.nasa.gov
- Fax your question to the NASA STI Help Desk at 301-621-0134
- Telephone the NASA STI Help Desk at 301-621-0390
- Write to:
NASA Center for AeroSpace Information (CASI)
7115 Standard Drive
Hanover, MD 21076-1320



Notch Fatigue Strength of a PM Disk Superalloy

*John Gayda, Timothy P. Gabb, and Jack Telesman
Glenn Research Center, Cleveland, Ohio*

Prepared for the
Materials Science and Technology 2007 Conference and Exhibit (MS&T'07)
cosponsored by the ACeRS, AIST, ASM, and TMS
Detroit, Michigan, September 16–20, 2007

National Aeronautics and
Space Administration

Glenn Research Center
Cleveland, Ohio 44135

This report contains preliminary findings,
subject to revision as analysis proceeds.

Level of Review: This material has been technically reviewed by technical management.

Available from

NASA Center for Aerospace Information
7115 Standard Drive
Hanover, MD 21076-1320

National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161

Available electronically at <http://gltrs.grc.nasa.gov>

Notch Fatigue Strength of a PM Disk Superalloy

John Gayda, Timothy P. Gabb, and Jack Telesman
National Aeronautics and Space Administration
Glenn Research Center
Cleveland, Ohio 44135

Introduction

New powder metallurgy (PM) disk superalloys, such as ME3 (ref. 1), LSHR (ref. 2), and Alloy 10 (ref. 3), have been developed in recent years which enable rim temperatures in turbine disk applications to approach 1300 °F. Before these alloys can be utilized at 1300 °F their long term durability must be ensured. One of the key requirements for disk rims is notch fatigue strength. This issue is extremely important and is a direct result of the blade attachment geometry employed at the disk rim. Further, the imposition of a dwell at maximum load, associated with take off and landing, can also compromise notch fatigue strength (ref. 1). For these reasons a study has been undertaken to assess the notch dwell fatigue strength of a modern PM disk alloy through spin pit evaluation of a prototypical disk. The first element of this program involves screening potential heat treatments with respect to notch fatigue strength at 1300 °F utilizing a conventional notch fatigue specimen with a stress concentration factor (K_t) of 2 and a 90 sec dwell at peak load. The results of this effort are reported in this paper including the downselect of an optimal heat treatment, from a notch fatigue standpoint.

Material and Procedures

The material selected for this program was LSHR, a 3rd generation PM superalloy, strengthened by about 60 percent gamma prime phase. The composition of LSHR is presented in table I. LSHR powder was produced using argon gas atomization and was consolidated via the hot isostatic pressing and extrude route to produce a 3.5 in. diameter billet. Mults cut from the billet were isothermally forged to produce pancake forgings about 6 in. in diameter and 1.5 in. in height. Six commercially viable heat treatments, presented in table II, were evaluated in this program. Four produced fine grain microstructures, about ASTM 11, utilizing a subsolvus solution step and two produced coarse grain microstructures, about ASTM 7, utilizing a supersolvus solution step. The subsolvus solution step was followed by an oil quench or a gas fan quench while the supersolvus solution step was followed by a gas fan quench. After the solution and quench, the forgings were given a single step age, 1425 °F/8 hr, or a two step age, 1570 °F/4 hr, and 1425 °F/8 hr. Each heat treat option was designed to produce a different mix of tensile, creep, and crack growth properties.

Standard mechanical tests were run at 1300 °F to verify the tensile, creep, and crack growth properties of each heat treat option. Creep tests were run at 115 ksi using a combo test bar presented in figure 1, while crack growth tests were run with a 90 sec dwell at peak load using a K_t specimen described in reference 4. Stress relaxation tests were also run employing tensile specimens which were loaded to and held at 1 percent strain for a minimum of 100 hr.

The notch dwell fatigue tests were run using the geometry depicted in figure 2. A low stress ground, longitudinal polish was employed to cut the notch and therefore minimize specimen to specimen variation associated with surface finish at the critical location. As previously stated, the specimen provided a K_t of 2. A peak, net section stress of 115 ksi was applied for 90 sec in each cycle as shown in figure 3. The selection of stress was aggressive but reasonable for a disk rim application. As these tests are quite lengthy, the initial screening matrix called for testing up to six specimens from each heat treat lot to failure or a 10,000 cycle runout condition, approximating the life requirement for turbine disks. A subsequent study will be undertaken to obtain fatigue lives of those specimens which exceed 10,000 cycles in duration.

Results and Discussion

The microstructure for each heat treat option is presented in figure 4. The features observed in these microstructures are in line with expectations. In addition to the grain size difference between the subsolvus and supersolvus heat treatments, the subsolvus microstructures contain micron size primary gamma prime. Also note, the oil quench produces a finer secondary gamma prime structure compared with the gas fan quench.

Tensile and creep test results are presented in tables III and IV, respectively. As with microstructure, the observed trends are in line with expectations. With respect to the tensile data, it is interesting to note the elongation for all heat treatments hover about 10 percent with the exception of H2 which approaches 20 percent. However, H2 also exhibits the lowest yield strength. Creep times to 0.2 percent and rupture lives of the combo bars are tabulated in table IV. All of the combo bars listed in table IV failed in the smooth section. The ranking of creep lives was in line with previous results for this alloy (ref. 2). Most notably, the two step aging sequence is seen to diminish creep capability, as gamma prime precipitate size coarsens. Stress relaxation data for the six heat treat options is presented in figure 5. As one might expect, the ranking for the stress relaxation data approximates the ranking for the creep data, i.e., microstructures prone to lower creep rates also maintained higher stress levels at a given time in the relaxation tests.

Dwell crack growth rates of the six heat treats are presented in figure 6. As with tensile and creep data, the ranking of crack growth rates was in line with previous data on LSHR. The six heat treats produced differences of over one order of magnitude in crack growth rates at 1300 °F, with the H2 microstructure being significantly better than all others.

Notch dwell fatigue testing of the first twelve specimens, two from each heat treat, produced very interesting results. Three of twelve failed in less than 1,000 cycles while all others reached the 10,000 cycle runout condition. Based on these results, the remaining 24 tests were run to a 2,000 cycle runout criteria to accelerate data acquisition and enhance statistics on the low life failure phenomenon, i.e., lives less than a 1,000 cycles. The results of all 36 tests are summarized in table V and figure 7. As seen in table V, the population of failures was bimodal, with 7 of 36 specimens failing in less than 1,000 cycles and the remaining specimens reaching the desired runout lives. Preliminary examination of the failed specimens did not reveal anything unusual on the fracture surface, i.e., no large pores or inclusions. Further fracture analysis is planned. In figure 7, the fraction of specimens which failed is plotted as a function of heat treat. As seen in this plot all the low life failures were confined to the J1 and H1 heat treat series. Recall J1 employs a subsolvus, oil quench heat treat while H1 employs a supersolvus, gas fan quench heat treat. Both J1 and H1 also employ a one step age, however, E1 also employs a one step age and did not exhibit the low life failure phenomenon. While the J1 and H1 heat treats are different in certain respects, they both produce microstructures with the best creep resistance and therefore are the most resistant to stress relaxation. This suggests that higher stress levels maintained during the dwell for J1 and H1 may have led to premature failure. Viscoplastic stress analysis of the specimen is being pursued to examine this issue in greater detail. Also, future plans call for continued testing of selected specimens to obtain finite lives beyond the 10,000 cycle runout criteria.

With respect to the spin pit experiment, the E2 heat treat has been selected for several reasons. First and foremost, it did not exhibit the low life failure phenomenon. Second, of the remaining heat treat options it represents a reasonable compromise between strength and crack growth resistance. More detailed testing on the E2 heat treat is planned to fully support the spin pit testing and analysis which is intended to demonstrate high temperature rim capability of LSHR.

Summary and Conclusions

Six potential heat treat options for a 3rd generation PM disk alloy, LSHR, were studied with respect to notch dwell fatigue strength at 1300 °F. Initial results showed two of the six heat treats, J1 and H1, exhibited a bimodal life distribution. The low life population for these two heat treats was less than 1,000 cycles, over one order of magnitude less than the lives of all other specimens tested. These two heat treats were also found to produce the highest creep strength for this alloy. Further work will be required to determine if this factor has contributed to the life deficit for these two heat treatments.

References

1. T.P. Gabb, J. Telesman, P. Kantzos, and K. O'Connor, "Characterization of the Temperature Capability of Advanced Disk Alloy ME3," NASA/TM—2002-211796, August 2002.
2. T.P. Gabb, J. Gayda, J. Telesman, and P. Kantzos, "Thermal and Mechanical Property Characterization of the Advanced Disk Alloy LSHR," NASA/TM—2005-213645, June 2005.
3. S. Jain, "Regional Engine Disk Process Development," NASA Contract NAS3-27720, September 1999.
4. R. Vanstone and T. Richardson, "Potential Drop Monitoring of Cracks in Surface Flaw Specimens," ASTM STP 877, 1985.

TABLE I.—COMPOSITION OF NICKEL-BASE
SUPERALLOY LSHR IN WEIGHT PERCENT

Co	Cr	Al	Ti	Mo	W	Nb	Ta	C	B	Zr
21.3	12.9	3.4	3.6	2.7	4.3	1.4	1.7	0.03	0.03	0.05

TABLE II.—HEAT TREATMENTS FOR LSHR

Code	Solution step, °F/hr	Quench	Age	
			°F/4 hr	°F/8 hr
J1	2075	Oil	-----	1425
J2	2075	Oil	1570	1425
E1	2075	Fan air	-----	1425
E2	2075	Fan air	1570	1425
H1	2140	Fan air	-----	1425
H2	2140	Fan air	1570	1425

TABLE III.—1300 °F TENSILE DATA FOR LSHR

Code	Yield, ksi	UTS, ksi	Elongation, percent	RA, percent
J1	170	199	6.5	9.5
J2	169	193	9.0	15
E1	163	191	7.0	11
E2	161	186	9.5	15
H1	155	197	13	16
H2	149	191	19	33

TABLE IV.—CREEP DATA FOR LSHR
AT 1300 °F AND 115 KSI

Code	0.2 percent creep, hr	Rupture, hr	Elongation, percent
J1	129	389	6.5
J2	15.7	159	8.9
E1	66.3	322	14.8
E2	9.4	142	13.0
H1	104	378	5.4
H2	17.1	277	6.5

TABLE V.—DWELL NOTCH FATIGUE RESULTS
FOR LSHR AT 1300 °F ($K_t = 2$)

Code	Heat treat	Life (cycles)
J1-N1	Subsolvus/oil/one step age	290
J1-N2	Subsolvus/oil/one step age	10,000+
J1-N3	Subsolvus/oil/one step age	68
J1-N4	Subsolvus/oil/one step age	102
J1-N5	Subsolvus/oil/one step age	2,000+
J1-N6	Subsolvus/oil/one step age	2,000+
J2-N1	Subsolvus/oil/two step age	10,000+
J2-N2	Subsolvus/oil/two step age	10,000+
J2-N3	Subsolvus/oil/two step age	2,000+
J2-N4	Subsolvus/oil/two step age	2,000+
J2-N5	Subsolvus/oil/two step age	2,000+
J2-N6	Subsolvus/oil/two step age	2,000+
E1-N1	Subsolvus/fan/one step age	10,000+
E1-N2	Subsolvus/fan/one step age	10,000+
E1-N3	Subsolvus/fan/one step age	2,000+
E1-N4	Subsolvus/fan/one step age	2,000+
E1-N5	Subsolvus/fan/one step age	2,000+
E1-N6	Subsolvus/fan/one step age	2,000+
E2-N1	Subsolvus/fan/two step age	10,000+
E2-N2	Subsolvus/fan/two step age	10,000+
E2-N3	Subsolvus/fan/two step age	2,000+
E2-N4	Subsolvus/fan/two step age	2,000+
E2-N5	Subsolvus/fan/two step age	2,000+
E2-N6	Subsolvus/fan/two step age	2,000+
H1-N1	Supersolvus/fan/one step age	194
H1-N2	Supersolvus/fan/one step age	368
H1-N3	Supersolvus/fan/one step age	2,000+
H1-N4	Supersolvus/fan/one step age	2,000+
H1-N5	Supersolvus/fan/one step age	663
H1-N6	Supersolvus/fan/one step age	562
H2-N1	Supersolvus/fan/two step age	10,000+
H2-N2	Supersolvus/fan/two step age	10,000+
H2-N3	Supersolvus/fan/two step age	2,000+
H2-N4	Supersolvus/fan/two step age	2,000+
H2-N5	Supersolvus/fan/two step age	2,000+
H2-N6	Supersolvus/fan/two step age	2,000+

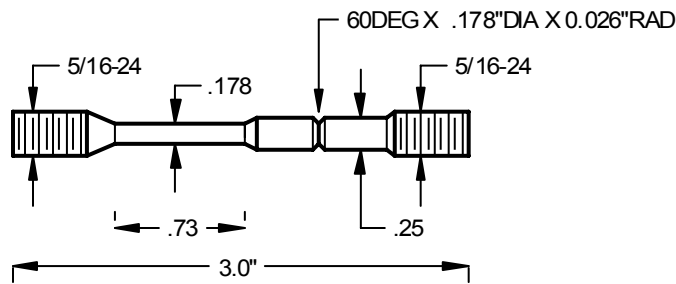


Figure 1.—Design of the creep combo bar. Notch feature of the creep combo bar employs same stress concentration factor as notch fatigue bar ($K_t = 2$).

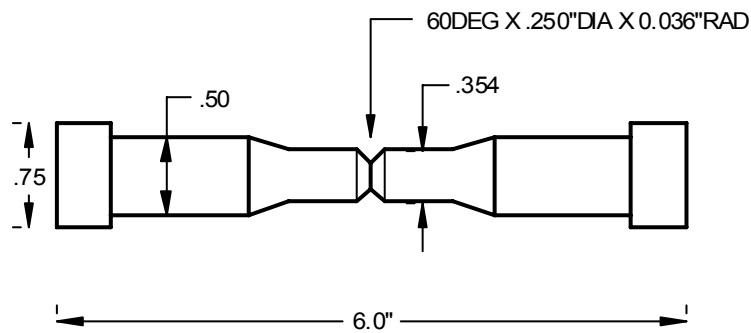


Figure 2.—Design of the notch fatigue specimen ($K_t = 2$). The notch was cut utilizing a low stress grind followed by a longitudinal polish at the base of the notch.

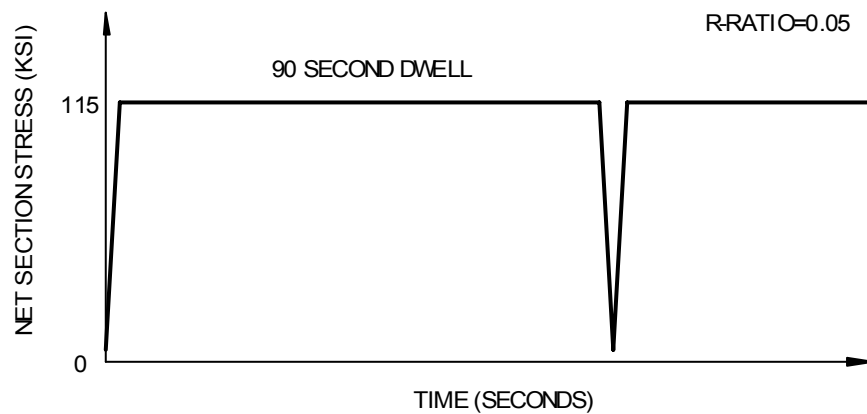


Figure 3.—Waveform of the dwell fatigue cycle employed in this study.

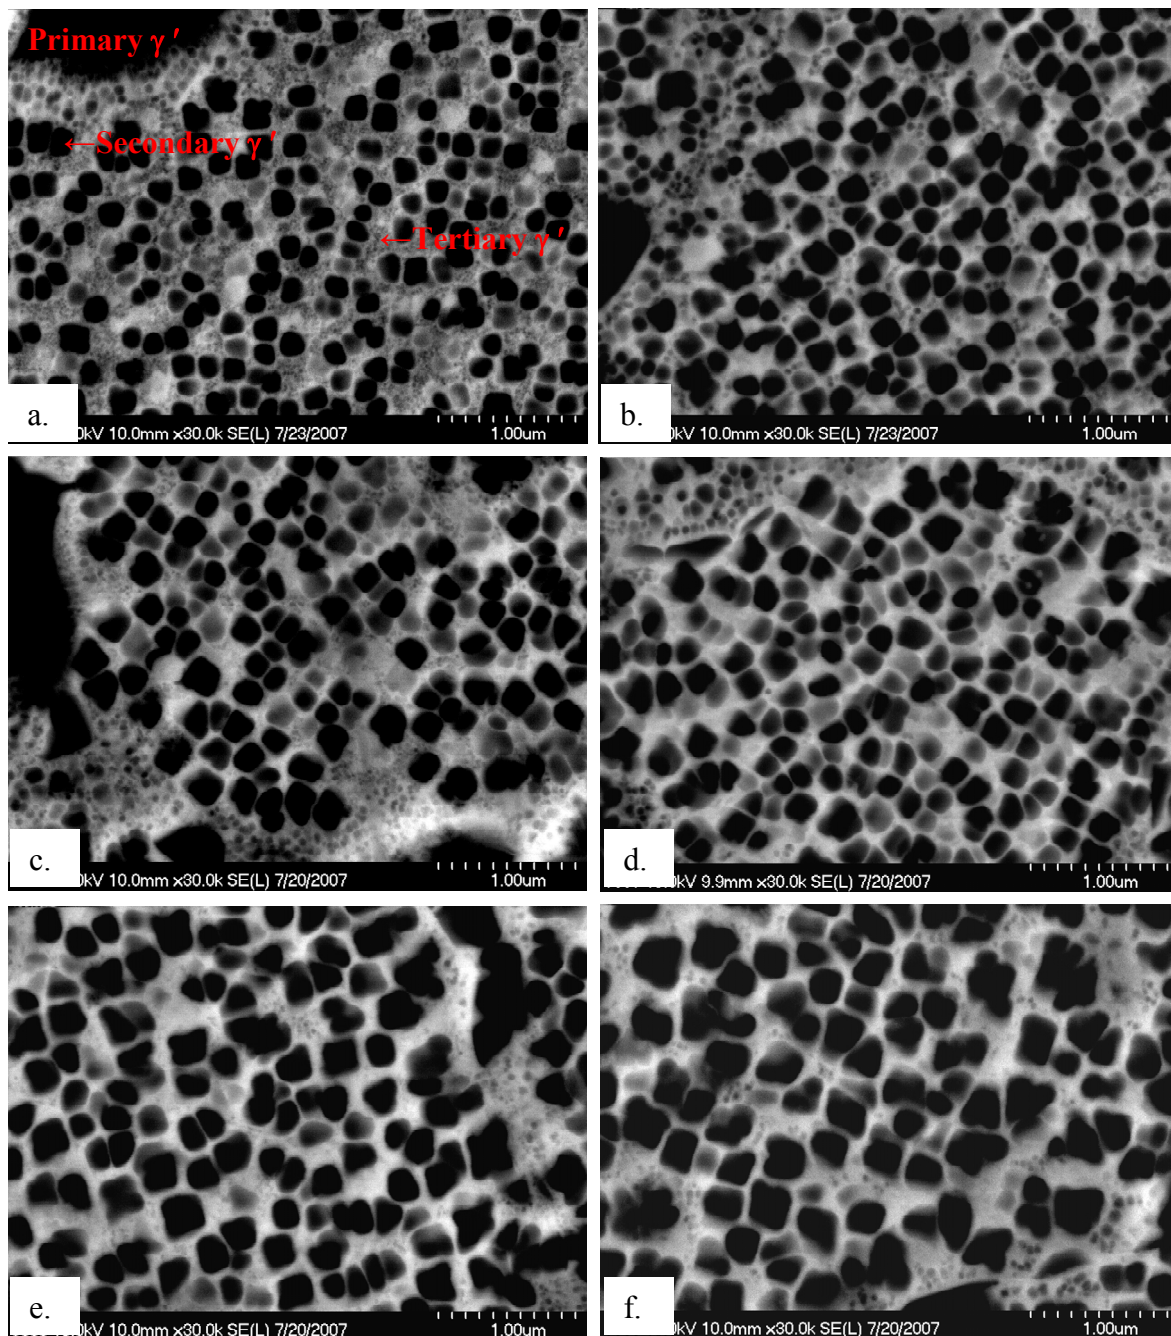


Figure 4.— γ' precipitate microstructures for LSHR after heat treatments: a. J1, b. J2, c. E1, d. E2, e. H1, and f. H2.

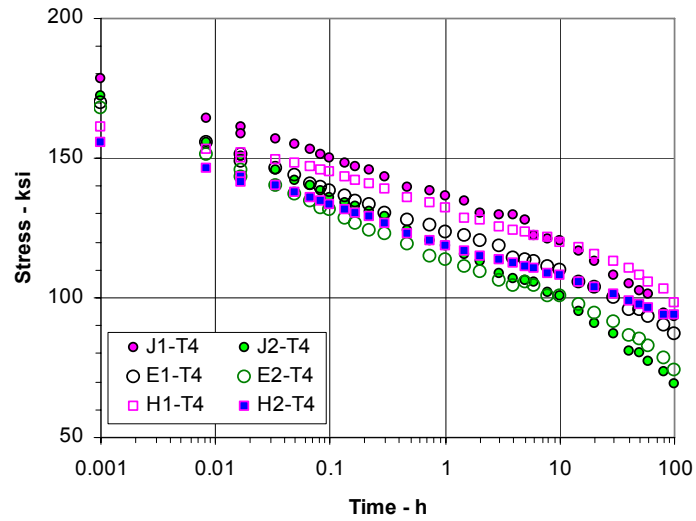


Figure 5.—Stress relaxation data for LSHR as a function of heat treat at 1300 °F. Specimens were loaded to and held at 1 percent strain while monitoring the rate of stress decay.

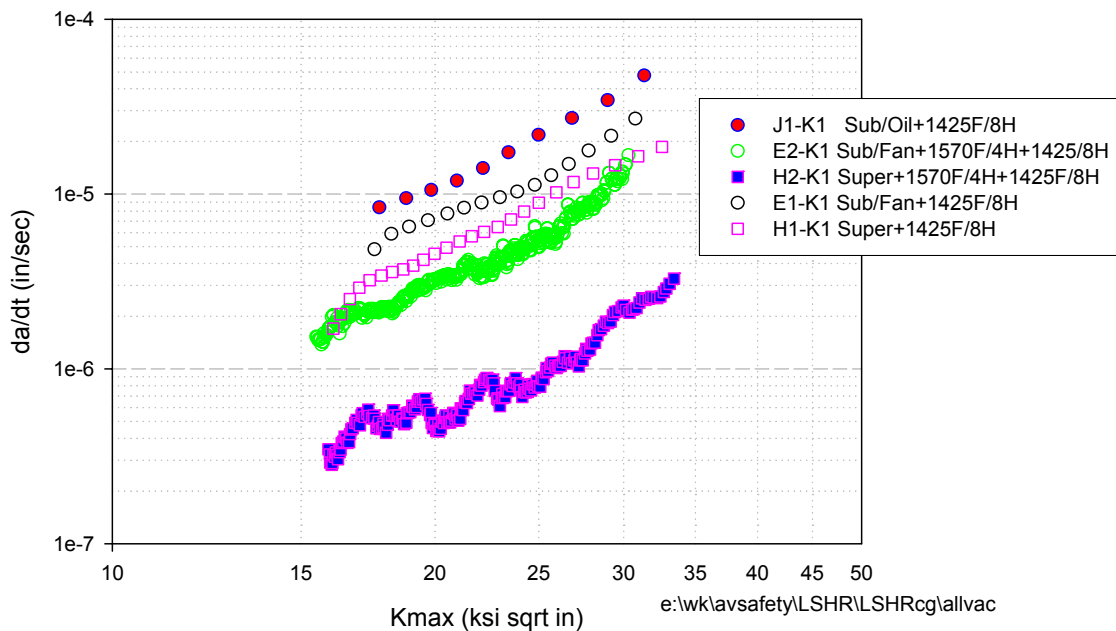


Figure 6.—Dwell crack growth data for LSHR as a function of heat treat at 1300 °F.

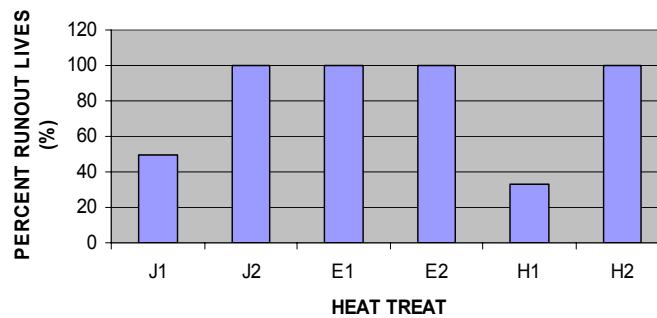


Figure 7.—Notch dwell fatigue data for LSHR at 1300 °F.

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
<p>The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.</p> <p>PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.</p>					
1. REPORT DATE (DD-MM-YYYY) 01-10-2007		2. REPORT TYPE Technical Memorandum		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE Notch Fatigue Strength of a PM Disk Superalloy				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Gayda, John; Gabb, Timothy, P.; Telesman, Jack				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER WBS 698259.02.07.03.04	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration John H. Glenn Research Center at Lewis Field Cleveland, Ohio 44135-3191				8. PERFORMING ORGANIZATION REPORT NUMBER E-16259	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001				10. SPONSORING/MONITORS ACRONYM(S) NASA	
				11. SPONSORING/MONITORING REPORT NUMBER NASA/TM-2007-215046	
12. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified-Unlimited Subject Category: 07 Available electronically at http://gltrs.grc.nasa.gov This publication is available from the NASA Center for AeroSpace Information, 301-621-0390					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT New powder metallurgy (PM) disk superalloys, such as ME3, LSHR, and Alloy 10, have been developed in recent years which enable rim temperatures in turbine disk applications to approach 1300 °F. Before these alloys can be utilized at 1300 °F their long term durability must be ensured. One of the key requirements for disk rims is notch fatigue strength. This issue is extremely important and is a direct result of the blade attachment geometry employed at the disk rim. Further, the imposition of a dwell at maximum load, associated with take off and landing, can also affect notch fatigue strength. For these reasons a study has been undertaken to assess the notch dwell fatigue strength of a modern PM disk alloy through spin pit evaluation of a prototypical disk. The first element of this program involves screening potential heat treatments with respect to notch fatigue strength at 1300 °F utilizing a conventional notch fatigue specimen with a stress concentration factor (K_t) of 2 and a 90 sec dwell at peak load. The results of this effort are reported in this paper including the downselect of an optimal heat treatment, from a notch fatigue standpoint.					
15. SUBJECT TERMS Gas turbine engines; Rotating disks; Heat resistant alloys; Fatigue (materials)					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES 13	19a. NAME OF RESPONSIBLE PERSON
a. REPORT U	b. ABSTRACT U	c. THIS PAGE U			STI Help Desk (email: help@sti.nasa.gov)
					19b. TELEPHONE NUMBER (include area code) 301-621-0390

